

Viability and Enzymatic Activity of Cryopreserved Porcine Heart Valve

Hwal Suh¹, Jong Eun Lee¹, Jong-Chul Park¹, Dong-Wook Han¹, Chee-Soon Yoon², Young Hwan Park², and Bum Koo Cho²

Abstract

Fibroblast viability of a natural tissue valve for replacing a defective heart valve through allograft or xenograft has been suggested to affect its clinical durability. In this study, the cell viability and enzymatic activity of porcine heart valve leaflets were examined in regard to concerning to the preservation process [variable warm ischemic time (WIT), cold ischemic time (CIT), and cryopreservation]. Porcine heart en blocs were obtained and valve dissection was performed after 2, 12, 24, or 36 hours, in respective groups A, B, C, and D, as WIT. Each group was stored for 24 hours as CIT and cryopreserved. Leaflets were dissected from a valved conduit after each process, and cell viability and enzymatic activity in the leaflet were investigated using trypan blue staining and API ZYM kits. WIT extension significantly decreased fibroblast viability ($p < 0.05$, $92.25 \pm 2.7\%$ at 2 hours, $84.9 \pm 6.7\%$ at 12 hours, $57.0 \pm 10.2\%$ at 24 hours, $55.9 \pm 7.9\%$ at 36 hours), while CIT for 24 hours was also influenced significantly ($p < 0.05$), whereas cryopreservation demonstrated no effect on cellular viability. In enzyme activity observation, several enzymes related to lipid or nucleotide degradation (esterase, esterase lipase, particularly phosphatase, phosphohydrolase) were remarkably changed following the valve-fabrication process. After 24 hours CIT, these enzymatic activities in groups B, C and D significantly increased, but the activities decreased after cryopreservation. Particularly, both the viability and enzymatic activity showed remarkable changes after CIT in group B (WIT=12 hours). These results suggest that WIT is more important than CIT in maintaining viability of the valve, and that completing all the cryopreservation process within 12 hours after acquisition is recommended.

Key Words: Porcine valve, viability, enzymatic activity, tissue preservation, cryopreservation

INTRODUCTION

The use of metallic valves or bioprosthetic tissue valves often produces serious clinical problems. Thrombogenesis and the consequent clinical side-effects can occur on metallic valves.¹ In comparison, a tissue valve for homograft or xenograft has several advantages such as freedom from coagulation, low incidence of thromboembolism, good physiologic performance, and relative resistance to endocarditis,²⁻⁴ however it has demonstrated less durability than a mechanical valve.⁵

To increase the durability of a tissue valve, glutaraldehyde has generally been used as a chemical cross-

linker for collagen to promote the stability of collagenous extracellular matrix of the tissue. But it has also been reported that a chemically-treated valve reveals less durability than homograft after implantation because of toxicity or calcification derived from the chemical reagent.^{6,7} By comparison, cryopreserved homograft has shown favorable clinical results after implantation, and the reason seems to be attributable to the viable fibroblasts in the valve.^{8,9} Viable fibroblasts synthesize the main constituents of extracellular matrix: collagen, elastin, reticulin and mucopolysaccharides;¹⁰⁻¹³ and therefore, the viability of fibroblasts in the implanted valve is related to the longevity of the implantation.

The preservation method of an acquired tissue influences the viability of fibroblast. Harvesting, the interval between arrest of the donor's heart and preservation of valves in refrigeration (the so-called warm ischemic time), sterilization, cryopreservation and thawing are the primary factors which affect the cellular physiology.¹⁴⁻¹⁶ All harvested valves have an obligatory period of ischemic time. The ischemic time is divided into warm ischemic time (WIT), which is

Received January 26, 1999

Accepted March 23, 1999

¹Department of Medical Engineering, ²Department of Cardiovascular Surgery, Yonsei University College of Medicine, Seoul, Korea
This study was supported by the Ministry of Health and Welfare of the Republic of Korea (Grant No. HMP-96-G-2-45).

Address reprint request to Dr. H. Suh, Department of Medical Engineering, Yonsei University College of Medicine, C.P.O. Box 8044, Seoul 120-752, Korea. Tel: 82-2-361-5406, Fax: 82-2-363-9923, E-mail: hwal@yumc.yonsei.ac.kr

defined as the interval from heart cessation until procurement of the heart, and cold ischemic time (CIT), which is the interval between procurement and dissection.¹⁷⁻¹⁸ This ischemic time has been shown to affect cell viability, but the time-dependent damage response of tissue valves has not been well characterized.

In this study, we investigated WIT-dependent damage to porcine leaflet tissue by investigating the fibroblast's viability and enzyme activities after 24 hours CIT and cryopreservation.

MATERIALS AND METHODS

Preservation of specimens

Thirty-two porcine heart-lung enblocs, consisting of blood-filled heart, lung, aorta, and vena cava, were obtained at a local slaughterhouse. The enblocs were preserved at 4–8°C in a refrigerator for 2, 12, 24, and 36 hours as WIT, and respectively assigned to groups A, B, C, and D. In each group, cellular viability and enzymatic activities were investigated after WIT, CIT and cryopreservation.

The left coronary valve leaflets were excised after each planned WIT. The remaining conduits were stored in Hartmann's solution (Choongwae Pharmacia Co. Seoul, Korea) at 4°C for 24 hours, and each non-coronary leaflet was excised to investigate the effects of 24-hours CIT. Subsequently, the last remaining conduits with the right coronary leaflets were disinfected in RPMI 1640 medium-antibiotic solution (cefoxitin 240 µg/ml medium; lincomycin 120 µg/ml; polymycin 100 µg/ml, vancomycin 50 µg/ml) at 4°C for 24 hours. The conduits were then cryopreserved for 2 weeks through a standard cryopreservation protocol. Specimens were placed in cryopreservation-bags containing RPMI 1640 medium supplemented with 10% fetal bovine serum (FBS) and 10% dimethyl sulfoxide (DMSO), and cryopreserved in a vapor phase of liquid nitrogen in a programmed freezer (MVE Cryogenics, Minneapolis, MI, USA). After 2 weeks, the valves were placed in a water bath at 40°C, and then stepwise dilution of DMSO for thawing was done.^{14,19} The thawed right coronary leaflets were used as the cryopreserved specimens.

Assessment of viability for fibroblasts

The leaflet was placed in an Eagle's minimum

essential medium (Eagle's MEM, Gibco BRL, Grand Island, NY, USA) containing 0.5% type II collagenase (350 units/mg solid, Sigma, St. Louis, MO, USA) at 37°C for 5 minutes. The endothelial layer was removed from the leaflet by gentle rubbing with a cell scraper and the tissue was minced with scissors after thorough washing with phosphate buffered saline (PBS) solution. The pieces were placed again in Eagle's MEM containing 0.5% type II collagenase and incubated in a shaking incubator at 37°C for 30 minutes. The suspension was then diluted with Eagle's MEM and centrifuged at 300 rpm for 5 minutes. The consequent supernatant was centrifuged again at 1000 rpm for 5 minutes and the obtained cell pellet was separated to dilute in Eagle's MEM. Fifty µl of 0.4% trypan blue solution (Gibco BRL, Grand Island, NY, USA) was added to 50 µl of cell suspension ($2 \times 10^5 - 10^6$ /ml). The number of cells not stained by trypan blue was immediately counted by a light microscope with a hemacytometer. The viability percentage of fibroblasts was recorded by subtracting the number of stained nonviable cells from the total number of cells.^{20,21}

The measurement of enzymatic activities

The enzymatic activities of 19 enzymes were observed to investigate the overall enzymatic change in tissue by using an API ZYM kit (Biomerieux Vitek Inc., Lyon, France) which detects a phosphatase alkaline, 3 lipases [esterase (C4), esterase lipase (C8), lipase (C14)], five peptidases [leucine arylamidase, valine arylamidase, cystine arylamidase, trypsin, chymotrypsin], a phosphatase acid, a phosphohydrolase, and 8 glucidases [α -galactosidase, β -galactosidase, β -glucuronidase, α -glucosidase, β -glucosidase, N-acetyl- β glucosaminidase, α -mannosidase, α -fucosidase]. Leaflet tissue was ground with a potter's tube, and suspended in 2 ml of sterilized distilled water. The suspension was centrifuged at 400 rpm, and the supernatant was retained as specimen. Sixty-five µl of specimen was inoculated into an API ZYM strip composed of 20 microtubes containing enzymatic substrate at the bottom. The strip was incubated for 4 hours at 37°C, and each one-drop of ZYM A and ZYM B was added to the strip. An enzyme reaction was graded from 0 to 5 (enzymatic score) according to the intensity of the colored reaction as compared with representations on a color chart.²² The enzymatic activity was represented by the quantity of hydrolyzed substrate that was determined by enzymatic score. To

secure an accurate comparison between specimens, the enzymatic score was calibrated by using the amount of protein in the loading specimen. The calibrated data revealed the value of enzyme activity per amount of protein (nmole/ μ g). Protein contents were determined by the Bradford method.²⁰ Enzymatic activity was not performed on group C after WIT due to

specimen deterioration.

Statistical analysis of data

Statistical analysis was performed using the statistical package SPSS-PC. One-way analysis of variance (ANOVA) followed by Turkey HSD tests for multiple comparisons were used to detect the effect of WIT on both the viability of fibroblast and the enzymatic activity of leaflets. Pearson correlation test was performed to identify a linear association between viability and WIT. In addition, the effect of cold ischemia or cryopreservation was also determined by using two-way ANOVA. The differences of enzymatic activity between experimental processes at each group were analyzed by one-way ANOVA or by t-test. A statistically significant difference was accepted as $p < 0.05$.

RESULTS

Fibroblast viability related to variable WIT, cold ischemia, and cryopreservation is shown in Fig. 1. As WIT increased from 2 hours to 36 hours, the cellular viability was reduced from $92.15 \pm 2.67\%$ to $55.88 \pm 7.88\%$, and a significant negative correlation was

Fig. 1. The effect of warm ischemic time, cold ischemia, and cryopreservation on fibroblast viability (%): *Groups demonstrated significantly decreased cell viability by one-way ANOVA ($p < 0.05$, *^A compared with group A, *^{A,B} compared with group A and B). **Cold ischemia remarkably influenced the viability ($p < 0.05$) by 2-way ANOVA, whereas cryopreservation did not ($p = 0.656$).

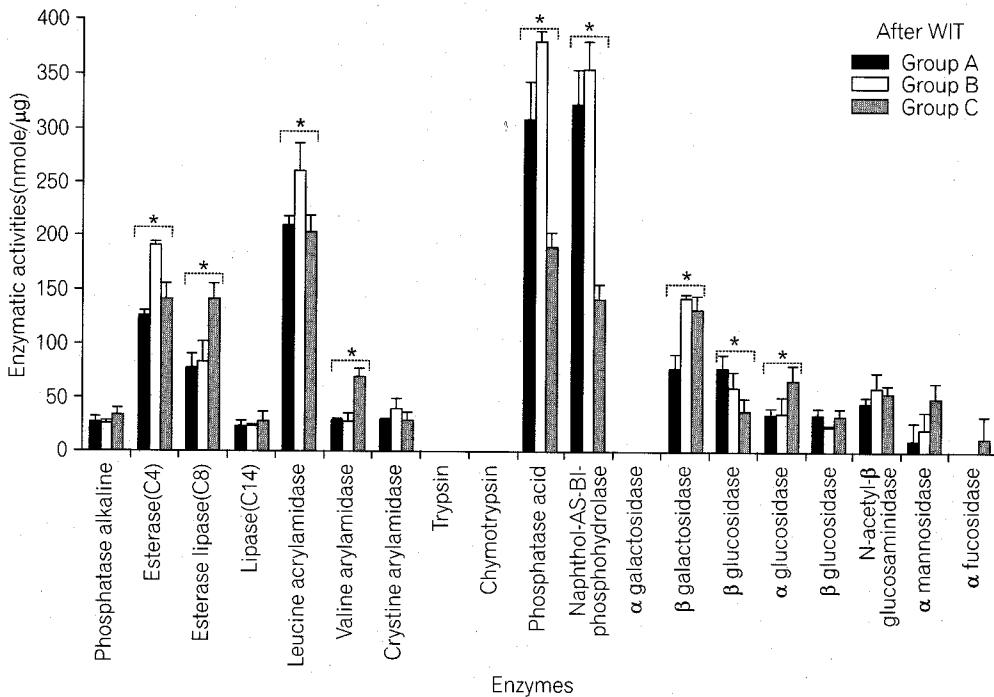
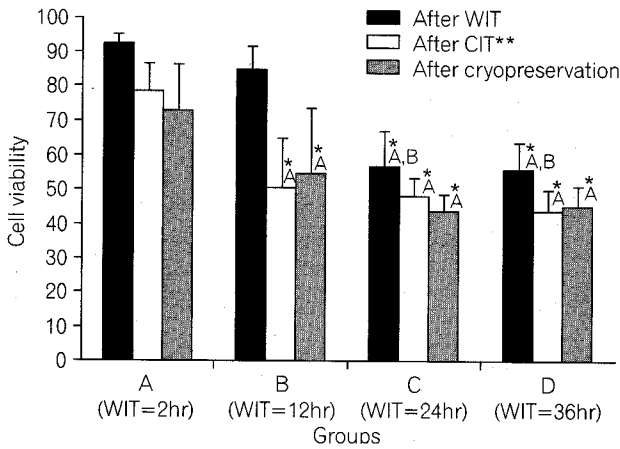


Fig. 2. The determination of enzymatic activities with various warm ischemic times: (* $p < 0.05$, significantly different between groups in each enzyme by one-way ANOVA).

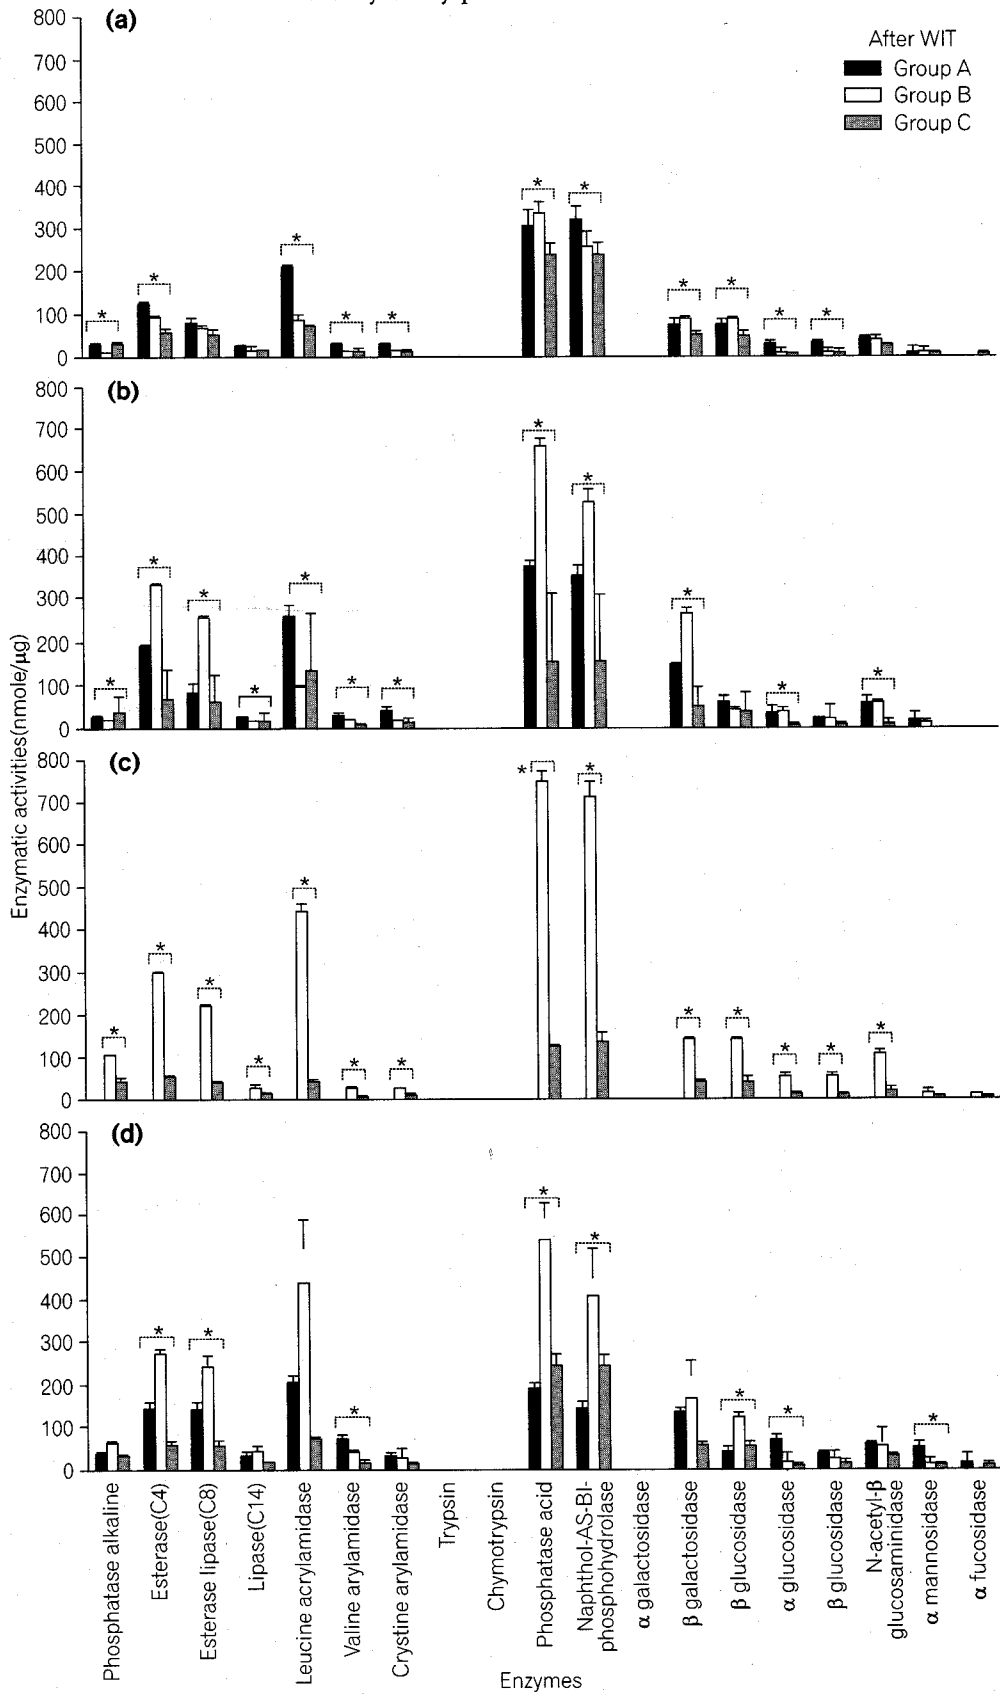


Fig. 3. The determination of enzymatic activities after cold ischemia, and cryopreservation. (a) group A, WIT=2, (b) group B, WIT=12, (c) group C, WIT=24 hours, and (d) group D, WIT=36. (* $p < 0.05$, significantly different between preservation processes in each enzyme by one-way ANOVA or by t-test).

group C after WIT, it could be predicted that the activities would be in correlation with the fibroblast viability. After cryopreservation, fibroblast viability was maintained as much as after CIT in trypan blue dye exclusion (Fig. 1). This result supports the brief that the use of liquid nitrogen for tissue storage is acceptable, and it is in agreement with the report that a heart valve leaflet stored at -196°C has been shown to be stable for at least 10 years.^{8,15} However, enzymatic activity decreased after cryopreservation in all the groups, and it suggested that intracellular enzymes, though viability was maintained, were deactivated during cryopreservation (Fig. 3).

In conclusion, the shorter WIT was, the more effectively the viability of fibroblast could be maintained. Cold ischemic condition for 24 hours provided changes in both fibroblast viability and enzymatic activity of leaflets on WIT less than 12 hours, but remarkably influenced them on WIT of more than 12 hours. Cryopreservation did not significantly affect the viability of fibroblasts. Therefore, it is suggested that a procured valve has to be transported and cryopreserved within 12 hours of WIT in consideration of 24 hours of cold ischemia.

REFERENCES

1. Pidisheim D, Wat'son JT. Cardiovascular applications. In: Ratner BD, Hoffmann AS, Schoen FJ, Lemons JE, editors. *Biomaterials Science*. San Diego: Academic Press; 1996. p.283-97.
2. Reul GJ Jr, Cooley DA, Duncan JM, Frazier OH, Hallman GL, Liversay JJ, et al. Valve failure with the Ionescu-Shiley bovine pericardial bioprosthesis: Analysis of 2680 patients. *J Vasc Surg* 1985;2:192-204.
3. Courtman DW, Pereira CA, Omar S, Langdon SE, Lee JM, Wilson GJ. Biomechanical and ultrastructural comparison of cryopreservation and a novel cellular extraction of porcine aortic valve leaflets. *J Biomed Mater Res* 1995;29:1507-16.
4. Crescenzo DG, Hilbert SL, Messier Jr RH, Domkowski PW, Barrick MK, Lange PL, et al. Human cryopreserved homografts: Electron microscopic analysis of cellular injury. *Am Thorac Surg* 1993;55:25-31.
5. Borkon AM, Soule LM, Banghman KL. Comparative analysis of mechanical and bioprosthetic valves after aortic valve replacement. *J Thorac Cardiovasc Surg* 1987;94:20-3.
6. Fiddler GI, Gerlis LM, Walker DR, Scott O, Williams GJ. Calcification of glutaldehyde-preserved porcine and bovine xenograft valves in young children. *Ann Thorac Surg* 1983;35:257-61.
7. Levy RJ, Schoen RJ, Anderson HC. Cardiovascular implant calcification: A survey and update. *Biomaterials* 1991;12:707-14.
8. Angell WW, Angell JD, Oury JH, Lamberti JJ, Grehl TM. Long-term follow-up of viable frozen aortic homografts. *J Thorac Cardiovasc Surg* 1987;93:815-22.
9. O'Brien MF, Mcgriffin DC, Stafford EG. Allograft aortic valve replacement: long-term comparative clinical analysis of the viable cryopreserved and antibiotic 4°C stored valves. *J Cardiac Surg* 1991;32 Suppl:534-43.
10. van der Kamp AWM, Navita J. Fibroblast function and the maintenance of the aortic-valve matrix. *Cardiovasc Res* 1979;13:167-72.
11. O'Brien MF, Stafford G, Gardner M, Pohlner P, Mcgriffin D, Johnston N, et al. The viable cryopreserved allograft aortic valve. *J Cardiac Surg* 1987;2 Suppl:153-67.
12. Hu JF, Gilmer L, Hopkins R, Wolfnibarger L Jr. Effect of antibiotics on cellular viability in porcine heart valve tissue. *Cardiovasc Res* 1989;23:960-4.
13. Hu JF, Gilmer L, Hopkins R, Wolfnibarger L Jr. Assessment of cellular viability in cardiovascular tissue as studied with ^3H proline and ^3H insulin. *Cardiovasc Res* 1990;24:528-31.
14. Bank HL, Brockbank KGM. Basic Principles of cryobiology. *J Cardiovasc Surg* 1987;2 Suppl:137-43.
15. Angell WW, Oury JH, Lamberti JJ, Koziol J. Durability of the viable aortic allograft. *J Thorac Cardiovasc Surg* 1989;98:48-56.
16. Wassenaar C, Bax WA, Suylen RJ van, Vuzevski VD, Bos E. Effect of cryopreservation on contractile properties of porcine isolated aortic valve leaflets and aortic wall. *J Thorac Cardiovasc Surg* 1997;113:165-72.
17. Crescenzo DG, Hilbert SL, Barrick MK, Corcoran PC, Louis JD St, Messier Jr RH, et al. Donor heart valves: electron microscopic and morphometric assessment of cellular injury induced by warm ischemia. *J Thorac Cardiovasc Surg* 1992;103:253-58.
18. Brockbank KGM, Dawson PE. Influence of whole heart postprocurement cold ischemia time upon cryopreserved heart valve viability. *Transplant Proc* 1993;25:3188-289.
19. Brockbank KGM, Carpenter JF, Dawson PE. Effects of storage temperature on viable bioprosthetic heart valves. *Cryobiology* 1992;29:537-42.
20. Freshney RI. Measurement of viability and cytotoxicity. In: *Culture of animal*. 3rd ed. New York: A John Wiley & Sons, Inc.; 1994. p.287-99.
21. Niwaya K, Sakaguchi H, Kawachi K, Kitamura S. Effect of warm ischemia and cryopreservation on cell viability of human allograft valves. *Ann Thorac Surg* 1995;60 Suppl:114-7.
22. Bousquet J, Marty JP, Coulob Y, Robinet-levy M, Cour P, Michel FB. Enzyme determination and rast inhibition assays for orchard grass (*dactylis glomerata*): A comparison of commercial pollen extracts. *Ann Allergy* 1978;41:164-277.
23. Jones KH, Stenft JA. An improved method to determine cell viability by simultaneous staining with fluorescein diacetate-propidium iodide. *J Histochem Cytochem* 1985;33:77-79.
24. Darnell J, Lodish H, Baltimore D. Tools of molecular cell biology: cells and organisms. In: *Molecular cell biology*. New York: Scientific American books; 1986. p.131-87.

25. Lang SJ, Giordane MS, Cardon-Cardo C, Summers BD, Staiano-Coico L, Hajjar DP. Biochemical and cellular characterization of cardiac valve tissue after cryopreservation or antibiotic preservation. *J Thorac Cardiovasc Surg* 1994;108:63-7.
 26. Domkowski PW, Messier RH Jr, Crescenzo DG, Aly HS, Abd-Elfattah AS, Hilbert SL, et al. Preimplantation alteration of adenine nucleotides in cryopreserved heart valves. *Ann Thorac Surg* 1993;55:413-9.
-