



저작자표시 2.0 대한민국

이용자는 아래의 조건을 따르는 경우에 한하여 자유롭게

- 이 저작물을 복제, 배포, 전송, 전시, 공연 및 방송할 수 있습니다.
- 이차적 저작물을 작성할 수 있습니다.
- 이 저작물을 영리 목적으로 이용할 수 있습니다.

다음과 같은 조건을 따라야 합니다:



저작자표시. 귀하는 원저작자를 표시하여야 합니다.

- 귀하는, 이 저작물의 재이용이나 배포의 경우, 이 저작물에 적용된 이용허락조건을 명확하게 나타내어야 합니다.
- 저작권자로부터 별도의 허가를 받으면 이러한 조건들은 적용되지 않습니다.

저작권법에 따른 이용자의 권리는 위의 내용에 의하여 영향을 받지 않습니다.

이것은 [이용허락규약\(Legal Code\)](#)을 이해하기 쉽게 요약한 것입니다.

[Disclaimer](#) 

**Effect of Dentin Bonding Agent Acidity
on Surface Microhardness of Mineral Trioxide Aggregate**

Yun-Hui Im

The Graduate School

Yonsei University

Department of Medicine

**Effect of Dentin Bonding Agent Acidity
on Surface Microhardness of Mineral Trioxide Aggregate**

A Master's Thesis

Submitted to the Department of Medicine
and the Graduate School of Yonsei University

in partial fulfillment of the
requirements for the degree of
Master of Medical Science

Yun-Hui Im

June 2021


**This certifies that the Master's Thesis
of Yun-Hui Im is approved.**



Thesis Supervisor: Ji-Hun Kim



Won-Gyun Chung



Yoon Lee

**The Graduate School
Yonsei University
June 2021**

감사의 글

학위 과정과 논문을 마치고 이 감사의 글을 쓸 수 있게 되어 기쁩니다. 먼저 갑작스러운 지도교수 변경에도 기꺼이 논문 지도해주신 김지훈 교수님 진심으로 감사드립니다. 바쁘신 와중에도 논문 진행에 많은 조언과 격려해 주셔서 감사합니다. 귀중한 시간 내어 논문 심사와 섬세한 지도해주신 정원균 교수님께 감사드립니다. 학과 일로 바쁘심에도 불구하고 항상 저희 보존과 식구들에게 마음 써주셔서 감사합니다. 실험 설계와 지원에 많은 도움을 주신 이윤 교수님께 감사드립니다. 2년간 근관치료학에 대해 많은 가르침 주시고, 멀리서도 항상 지켜 봐주시고 가르쳐 주셔서 감사합니다. 힘든 시기에 옆에서 돌봐 주시고 마음 써주신 이정섭, 이천의 교수님께도 감사드립니다.

통계분석에 많은 도움을 준 사랑하는 친구 윤소라에게도 고마움을 전합니다. 3년간 수련 생활을 함께하며 많은 응원과 조언을 해주었던 의국 선후배 선생님들께 감사의 말씀 전합니다. 후배로서 많이 배울 수 있었던 박준성 선생님, 김민태 선생님, 이동재 선생님께 감사드립니다. 부족한 환경에서도 항상 열심히 진료 보고, 옆에서 많이 도와준 보존과 후배 선생님들 감사합니다.

마지막으로 항상 묵묵히 저를 지켜 봐주고 응원해주며, 가장 큰 버팀목이 되어주는 엄마, 아빠, 소라언니, 아라언니, 동생 하령이, 그리고 진우 오빠에게 진심으로 사랑한다고 감사의 말을 전합니다.

2021년 6월 저자 씀

Table of Contents

List of Figures	ii
List of Tables	iii
Abstract	iv
I. Introduction	1
II. Materials & Methods	4
1. Experimental groups.....	4
2. Specimen preparation.....	6
3. Surface microhardness measurements.....	7
4. Statistical analysis.....	7
III. Results	8
IV. Discussion	11
V. Conclusions	16
References	17
Abstract in Korean	21

List of Figures

Fig. 1. Mean Vickers microhardness (HV) of each group.....	10
Fig. 2. Mean Vickers microhardness (HV) of each point.....	10

List of Tables

Table 1. Materials used in this study.....	5
Table 2. Mean Vickers microhardness(HV) and standard deviation.....	9

ABSTRACT

Effect of Dentin Bonding Agent Acidity on Surface Microhardness of Mineral Trioxide Aggregate

Mineral trioxide aggregate (MTA) is a biocompatible dental material used in vital pulp therapy and root perforation repair. MTA has some disadvantages such as its a long setting time, difficulty of manipulation, and potential of discoloration of teeth. Previous studies have reported that the use of dentin bonding agents prevent tooth discoloration caused by MTA. While MTA surface hardness is known to be affected by acidity, no research has been conducted on the effect of the acidity of dentin bonding agents on the MTA surface hardness. This study investigates the effect of dentin bonding agent acidity on surface microhardness of MTA.

Forty cylindrical molds (3mm x 5mm) were prepared, and three dentin bonding agents with different acidities; Adper Single Bond 2 (ASB), Single Bond Universal (SBU), and Clearfil SE bond 2 (CSE) were applied to the inner surface of the molds (n=10). The control group was not applied any bonding agent. MTA was mixed and inserted into the prepared molds and sealed with a wet cotton pellet for 4 days. After confirming setting, the Vickers microhardness test was carried out at 200, 400, 600 μm from the inner surface of the mold. One-way ANOVA was conducted for all samples. A p-value less than .05 was considered

statistically significant. Tukey HSD test was performed to assess the differences between the groups.

The mean Vickers microhardness(HV) values and standard deviations of each group were 67.02 ± 11.38 (Con), 48.76 ± 11.33 (ASB), 43.78 ± 11.19 (CSE), 37.84 ± 9.36 (SBU), respectively. The difference between the control group and the experimental groups was statistically significant ($p < 0.001$). The difference between ASB and SBU was statistically significant ($p < 0.001$). However, the difference between SBU and CSE was not statistically significant. There were no statistically significant differences between the various points (200, 400, and 600 μ m) from the inner surface of the mold within each group ($p > 0.05$).

Results of the current study indicate that use of dentin bonding agents with MTA can reduce the surface microhardness of MTA. Moreover, there is a direct relationship between the acidity of dentin bonding agents and the surface microhardness of MTA.

Keywords : Mineral trioxide aggregate(MTA), dentin bonding agents, acidity, Vickers surface microhardness, discoloration

Effect of Dentin Bonding Agent Acidity on Surface Microhardness of Mineral Trioxide Aggregate

Yun-Hui Im, D.D.S.

Department of Medicine

The Graduate School, Yonsei University

(Directed by Prof. Ji-Hun Kim, D.D.S., M.S.D., Ph.D.)

I. Introduction

Mineral trioxide aggregate (MTA) is a biocompatible dental material which has been used in vital pulp therapy and root perforation repair since its introduction as a retrograde filling material in 1993.¹⁻³ MTA shows superior sealing and antibacterial properties compared to conventional retrograde materials. However, it has disadvantages such as a long setting time, difficulty of manipulation, and potential of discoloration of teeth. White MTA with a reduced ratio of metal oxides was introduced to facilitate the use of MTA in aesthetically important areas such as the anterior teeth.⁴ The color of the MTA was improved, but bismuth oxide contained in the product to make the material radiopaque maintains its oxidizing properties which induce discoloration.⁵⁻⁹ Despite the use of White MTA, discoloration of teeth was still observed. Studies report that the use of dentin bonding

agents reduces or prevents discoloration caused by MTA.^{7, 8, 10} Results of these studies indicate that the use of dentin bonding agents may be clinically beneficial to prevent discoloration caused by MTA. However, no research has been conducted to determine whether dentin bonding agents affect MTA and dental pulp in clinical situations such as vital pulp therapy.

MTA is an aggregate which changes as it is hydrated. The hydration process hardens the cement. That is, the hydration rate represents the hardening rate. The porosity, which is an indicator of the degree of hydration, can be confirmed through SEM images.^{11, 12} Vickers microhardness (HV) is defined as the resistance to plastic deformation after indenting the surface of a material. Vickers test was originally used to measure metals, but it is also used for various other materials such as ceramics and cement pastes. Hardness tests display the bulk properties of materials and are used to evaluate mechanical properties sensitive to microstructural traits such as changes in the ratio of water to cement.¹³ Although surface microhardness does not represent all the material properties of MTA, linear relationships between microhardness and compressive strength, porosity, and modulus of elasticity have been demonstrated.¹⁴ Surface microhardness is a non-destructive test that can be used as an indicator of the degree of hydration during hardening.¹³ The surface hardness of MTA is affected by various factors such as the pH value of the environment, the thickness of the material, the condensation pressure, the amount of entrapped air in the mixture, humidity, acid etching treatment, and temperature.¹⁵

Studies on bonding to MTA indicate that bonding process has several effects on MTA. Total-etch system shows higher bonding strength to MTA than the self-etch system.^{16, 17} In the presence of bonding agent, gap was not observed between MTA and composite resin, but gap was observed in the absence of bonding agent.¹⁵ In addition, acid-etching affects the micromorphology and adhesion of MTA, compressive strength, and surface microhardness.^{12, 18-20} However, has been no research published on the effect of light-cured bonding agents on MTA.

If bonding agents are to be used in the clinical context, such as vital pulp therapy, the effect of the agent's acidity on MTA microhardness should be explained. Based on the lack of data investigating the effect of dentin bonding agents on MTA, the purpose of the current study is to investigate the effect of dentin bonding agent acidity on the surface microhardness of MTA. The null hypothesis was that there are significant differences in surface microhardness of MTA depending on the acidity of the dentin bonding agents, and there are significant differences in surface microhardness of MTA between distances from bonding surface.

II. Materials and methods

Experimental groups

The experiments were conducted using the following dentin bonding agents: Adper Single Bond 2 (ASB; 3M ESPE, St. Paul, USA) which is a two-step total-etch bonding system with a pH of 4.7, Single Bond Universal (SBU; 3M Deutschland GmbH, Germany) which is a universal adhesive with a pH of 2.7, and Clearfil SE bond 2 (CSE; Kuraray Noritake Dental Inc, Japan) which is a two-step self-etch bonding system with a pH of 2.0 (primer) (Table 1). The MTA used was ProRoot® MTA (White) (Dentsply Tulsa Dental, USA)

Experiments were conducted in the following four groups (n=10);

Con: No bonding agent (control)

ASB: Adper Single Bond 2

SBU: Single Bond Universal

CSE: Clearfil SE bond 2

Table 1. Materials used in this study

Material	Abbreviation	pH	Composition	Lot number
ProRoot® MTA (white) (Dentsply Tulsa Dental, USA)	MTA	-		0000249677
Adper Single Bond 2 (3M ESPE, St.paul, USA)	ASB	4.7	Dimethacrylate Resins, HEMA, Vitrebond™ Copolymer, Filler, Ethanol, Water, Initiators	NC24034
Single Bond Universal (3M Deutschland GmbH, Germany)	SBU	2.7	MDP, Dimethacrylate Resins, HEMA, Vitrebond™ Copolymer, Filler, Ethanol, Water, Initiators, Silane	00221A
Clearfil SE bond 2 (Kuraray Noritake Dental Inc, Japan)	CSE	2.0	Primer: MDP, HEMA, Hydrophilic aliphatic dimethacrylate, dl- Camphorquinone, Water Bond: MDP, HEMA, Bis-GMA, Hydrophobic aliphatic dimethacrylate, dl- Camphorquinone Initiators, Accelerators, Silanated colloidal silica	1T0617

HEMA: 2-hydroxyethylmethacrylate; MDP: methacryloyloxydecyl dihydrogen phosphate; Bis-GMA: Bisphenol A diglycidylmethacrylate;

Specimen preparation

For the control group, ProRoot MTA was mixed according to the manufacturer's instructions; 0.34 g of liquid and 1 g of MTA was placed in a clean, empty amalgam capsule. The capsule was mixed for 30 seconds using amalgamator (D-650, TPC Advanced Technology Inc., City of Industry, CA, USA). A cylindrical mold (length 5 mm× diameter 3 mm) was placed on a glass plate and mixed MTA was inserted into the cylindrical mold.

For the experimental groups, three dentin bonding agents (ASB, SBU, CSE) were applied to inner surface of the cylindrical molds. After bonding agent treatment, MTA was mixed and inserted into the molds. For ASB and SBU groups, one layer of dentin bonding agent was applied in mold according to the manufacturer's instructions; ASB and SBU were applied and gently air thinned for 5 seconds to evaporate solvents, then light cured for 10 seconds. For the CSE group, two layers of dentin bonding agent were applied in mold according to the manufacturer's instructions; a CSE primer was applied for 20 seconds, and the volatile ingredients were evaporated with a mild oil-free air stream. Then, the CSE bonding agent was applied and the excess was scattered with a gentle air stream, followed by light curing for 10 seconds.

The specimens were then covered by a wet cotton pellet and a damp paper towel in a sealed plastic container and maintained for 4 days at room temperature with 95% humidity.²¹ The specimens were wet polished using a Buehler Ecomet 250 Grinder Polisher (Buehler, Lake Bluff, IL, USA) with minimal pressure. Polishing was performed with 400-grit, 800-grit, 1200-grit, and 2000-grit silicon carbide grinding papers.

Surface microhardness measurements

The investigated parameter was Vickers microhardness. For the measurement of the microhardness, polished surface of each sample was loaded with a diamond indenter point (MMT-X, Matsuzawa, Akita, Japan) with a weight of 50 g for 5 seconds dwell time.^{12, 15} The Vickers microhardness of each sample was calculated by measuring the diagonal diameter of the resulting indentation. Microhardness was calculated using the following equation.²² :

$$HV = \frac{2F \sin \frac{136}{2}}{d^2} \approx 1.854 * \frac{F}{d^2}$$

where F = load, 1.854 = Vickers constant, d = the mean of the two diagonals.

Each specimen sample was measured at three points at 200 micrometers intervals from the inner surface of the molds.

Statistical analysis

The mean microhardness value was calculated for each specimen. Data were analyzed using a R studio statistical software (ver0.99.903). One-way ANOVA was conducted, where a p-value less than .05 was considered statistically significant. The Tukey HSD test was then performed to assess differences between the groups.

III. Results

Surface microhardness

In order of highest to lowest, the mean Vickers surface microhardness (HV) values of the control group, ASB, CSE, and SBU groups were 67.02 ± 11.38 , 48.76 ± 11.33 , 43.78 ± 11.19 , 37.84 ± 9.36 , respectively (Table 2). There was a statistically significant difference between the groups under the 95% confidence level. Tukey's post hoc test revealed that the difference between the control group and the other experimental groups was statistically significant ($p < 0.001$). The difference between the ASB and SBU groups was statistically significant ($p < 0.001$), but the difference between the SBU and CSE groups was not. Moreover, there was no statistically significant difference in surface microhardness between the 200 μm , 400 μm , and 600 μm points within each group ($p > 0.05$) (Fig.2). However, there was a statistically significant difference in surface microhardness between groups at each point ($p < 0.05$). At each point, the control group showed higher values than all experimental groups, except for the ASB group at the 400 μm point ($p < 0.05$).

Table2. Mean Vickers microhardness(HV) and standard deviations (SD)

Group	Point(μm)	HV	SD
Control (n=10)	mean	67.02	11.38
	200	74.27	8.93
	400	63.54	14.04
	600	63.24	7.91
ASB (n=10)	mean	48.76	11.33
	200	45.26	9.77
	400	53.27	12.87
	600	47.65	10.65
SBU (n=10)	mean	37.84	9.36
	200	37.94	6.59
	400	38.18	12.25
	600	37.42	9.25
CSE (n=10)	mean	43.78	11.19
	200	42.03	9.98
	400	44.79	8.79
	600	44.51	15

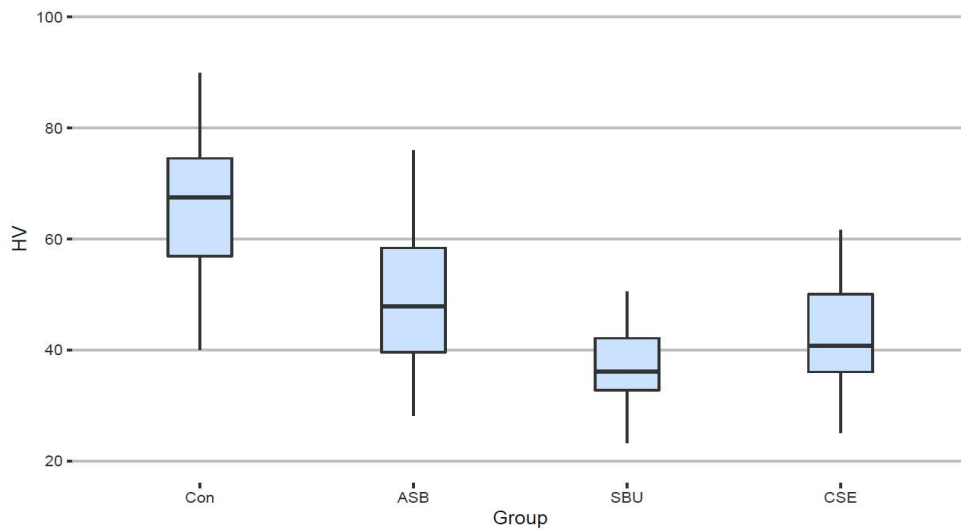


Figure 1. Mean Vickers microhardness (HV) of each group

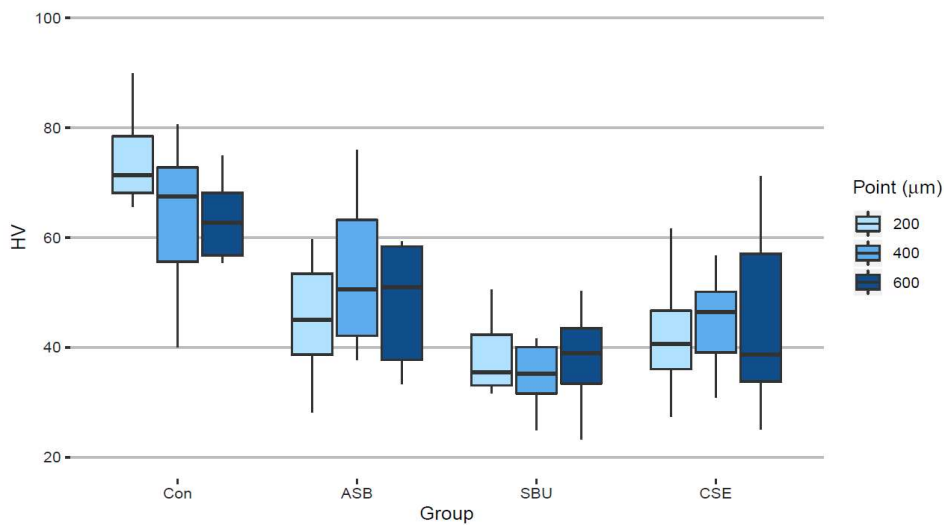


Figure 2. Mean Vickers microhardness (HV) of each point

IV. Discussion

The purpose of this study was to investigate the effect of dentin bonding agent according to its acidity on MTA surface microhardness. Materials based on calcium silicate are used in vital pulp therapy and perforation repair. After treatment, a cavity is filled with a final restoration. At this time, acid etching and dentin bonding agents are used. MTA properties such as solubility, compressive strength, hardness can be affected by the surrounding environment including acid etching and dentin bonding agents. The pH of dental adhesives used during treatment affect the microstructure and surface hardness of MTA, even after hardening.

Dry particles of MTA are hydrated and crystallized with interlocking mass. Crystallization occurs by the formation of cubic and needle-like crystals.¹¹ When it is hydrated by a solution with a pH 7, the cubic, needle-like structure is maintained. However, normal crystal structure is not maintained when MTA is hydrated with a pH 5 acidic solution. Moreover, when MTA is stored in a low pH solution, it has low microhardness.^{12,}²³ Studies have also reported that etching above hardened MTA increases microcracks on the surface and reduces surface hardness.¹⁸ MTA treated with phosphoric acid shows surface cracks and interior holes, and the lamellar structure disappears. Even treated with a self-etching primer, MTA shows no lamellar structure, and larger pores.¹⁹ However, no research has been carried out on the effect of light-cured bonding agents before MTA hardening.

In this experiment, the surface microhardness of the control group was higher than that of the other groups. The mean HV value of the control group was 67.02 ± 11.38 and the mean HV values of the experimental groups were 48.76 ± 11.33 (ASB), 37.84 ± 9.36 (SBU), and 43.78 ± 11.19 (CSE). The pH of each group was 4.7 (ASB), 2.7 (SBU), and 2.0 (CSE), respectively. The experimental groups were more acidic than the control group. ASB and SBU contain a Vitrebond™ Copolymer which is a polyalkenoic acid copolymer that chemically binds to calcium of tooth.²⁴ SBU and CSE contain MDP which imparts acidic characteristics.²⁵ Even if bonding agents are cured, an acidic environment can be created because unreacted monomers remain in the oxygen inhibition layer.²⁶ Previous studies have shown that exposure of MTA to acidic environments reduces its microhardness.^{11, 12, 20, 23} It has been demonstrated that MTA exposed to acidic environments shows no needle-like structures and incomplete cubic structures.¹¹ An acidic environment dissolves the needle-like crystal structure quickly and weakens the hardness of MTA.

In the current study, surface microhardness was significantly lower in the SBU group compared to the ASB group probably because SBU has lower pH value (pH 2.7) than that of ASB (pH 4.7). Thus, it can be inferred that the lower the pH, the lower the microhardness. Nevertheless, in the current experiment, CSE (pH 2.0), which has lower pH than SBU (pH 2.7), showed higher microhardness than SBU, although it was not statistically significant. We speculate that these results may be due to the pH of CSE bonding agent (unknown), and not the CSE primer (pH 2.0) itself. Previous research has demonstrated that MTA shows higher Vickers microhardness when stored in moist conditions compared with when

it is stored in dry conditions.²⁷ In addition, solvated adhesive show higher water sorption than solvent-free adhesives.²⁸ Therefore, SBU, which is a solvated adhesive, absorbs more water, thus creating a dry environment which may result in a low MTA microhardness. The null hypothesis that there are significant differences in surface microhardness of MTA depending on the acidity of the dentin bonding agents was partially accepted.

In the current study, there were no differences in surface microhardness of MTA between the 200, 400, and 600 μm points from the inner surface of the mold. Thus, the null hypothesis that there are significant differences in surface microhardness of MTA between distances from the bonding surface was rejected. During specimen preparation, MTA was inserted into a mold and a wet cotton pellet and paper towel were placed on the top, then the specimens were maintained in a sealed plastic container for four days. It is speculated that the cotton pellet itself creates an overall acidic environment, and this may be the reason that there were no significant differences in surface microhardness of MTA between distances.

The application of dentin bonding agents is limited in the clinical conditions; bonding agents are applied to the dentin inside the access cavity with a canal opening. ASB is a fifth generation adhesive that uses the two-step total etch technique which requires the use of etchant and rinses before a bonding agent is applied. During this process, etchant may flow into the canal. SBU is a seventh generation universal adhesive with two application modes: the self-etch mode and the total etch mode. According to data provided by the manufacturer, a higher dentin bonding strength can be obtained when the product is used in the self-etch

mode. However, according to other publications, there is no significant difference in bond strength between application modes, both of which are reliable. It is useful to apply it several times using the self-etch mode for a long time.²⁹⁻³² Both SBU and CSE bonding agents have low pHs. It is believed that dental adhesive systems of low pH may weaken the structure of MTA to a higher degree than those with a higher pH. Thus, further research on the clinical use of dentin bonding agents along with MTA is needed.

The pH of MTA is about 12.5 which is attributed to its antimicrobial properties and hard tissue formation capacity.³³ MTA stored in acidic pH solutions increases silicon and calcium ion release.³⁴ Silicon and calcium ion imply osteogenic and odontogenic potential. However, this increase in ion emission means greater solubility which may affect the sealing properties and surface hardness of MTA. Calcium silicated bioceramics such as MTA form calcium-phosphate salts when they meet phosphoric acid solutions. Hydroxyapatite formation capacity is an important factor in determining bioactivity. Acidic environments not only inhibit the formation of hydroxyapatite but also reduce cell viability. Further research is needed to determine whether dentin bonding agents used with MTA have an effect on another characteristic of MTA when an acidic environment is produced.

In this study, plastic cylinder molds were used. If the experiment was conducted using dentin substrate, as in clinical situations, the results may have been different. Self-etching primers of low pH values increase in pH when in contact with dentin. In particular, functional monomers in a primer form insoluble particles when in contact with dentin.^{35, 36}

Thus, if the experiment had used dentin substrate, the pH of the primer would have been offset and increased, which would have minimally effected the MTA.

V. Conclusions

Within the limitations of this study, three dentin bonding agents applied before MTA setting reduce microhardness of MTA. The higher acidity of dentin bonding agents may lead to the lower MTA microhardness. In clinical situation, it is recommended that MTA before setting is kept away from dentin bonding agent.

References

1. Torabinejad M, Watson T, Ford TP. Sealing ability of a mineral trioxide aggregate when used as a root end filling material. *Journal of endodontics* 1993;19:591-5.
2. Lee S-J, Monsef M, Torabinejad M. Sealing ability of a mineral trioxide aggregate for repair of lateral root perforations. *Journal of endodontics* 1993;19:541-4.
3. Parirokh M, Torabinejad M. Mineral trioxide aggregate: a comprehensive literature review—part I: chemical, physical, and antibacterial properties. *Journal of endodontics* 2010;36:16-27.
4. Asgary S, Parirokh M, Eghbal MJ, Brink F. Chemical differences between white and gray mineral trioxide aggregate. *J Endod* 2005;31:101-3.
5. Belobrov I, Parashos P. Treatment of tooth discoloration after the use of white mineral trioxide aggregate. *J Endod* 2011;37:1017-20.
6. Camilleri J. Color stability of white mineral trioxide aggregate in contact with hypochlorite solution. *Journal of endodontics* 2014;40:436-40.
7. Akbari M, Rouhani A, Samiee S, Jafarzadeh H. Effect of dentin bonding agent on the prevention of tooth discoloration produced by mineral trioxide aggregate. *Int J Dent* 2012;2012:563203.
8. Choi YL, Jang YE, Kim BS, Kim JW, Kim Y. Pre-application of dentin bonding agent prevents discoloration caused by mineral trioxide aggregate. *BMC Oral Health* 2020;20:163.
9. Marciano MA, Costa RM, Camilleri J, Mondelli RF, Guimaraes BM, Duarte MA. Assessment of color stability of white mineral trioxide aggregate angelus and bismuth oxide in contact with tooth structure. *J Endod* 2014;40:1235-40.
10. Razzaq FA, Mahdee AF. Effect of Dentine Bonding and Laser on Prevention of Teeth Discoloration Produced by Gray Mineral Trioxide Aggregate and Triple Antibiotic Paste: A Comparative In vitro Study. *Journal of Research in Medical and Dental Science* 2020;8:187-94.
11. Lee Y-L, Lee B-S, Lin F-H, Lin AY, Lan W-H, Lin C-P. Effects of physiological environments on the hydration behavior of mineral trioxide aggregate. *Biomaterials* 2004;25:787-93.

12. Namazikhah MS, Nekoofar MH, Sheykhrezae MS, Salariyeh S, Hayes SJ, Bryant ST, et al. The effect of pH on surface hardness and microstructure of mineral trioxide aggregate. *Int Endod J* 2008;41:108-16.
13. Igarashi S, Bentur A, Mindess S. Microhardness testing of cementitious materials. *Advanced Cement Based Materials* 1996;4:48-57.
14. Beaudoin JJ, Feldman RF. A study of mechanical properties of autoclaved Calcium silicate systems. *Cement and concrete research* 1975;5:103-18.
15. Tsujimoto M, Tsujimoto Y, Ookubo A, Shiraishi T, Watanabe I, Yamada S, et al. Timing for composite resin placement on mineral trioxide aggregate. *J Endod* 2013;39:1167-70.
16. Atabek D, Sillelioglu H, Ölmez A. Bond strength of adhesive systems to mineral trioxide aggregate with different time intervals. *Journal of endodontics* 2012;38:1288-92.
17. Bayrak S, Tunç ES, Saroglu I, Egilmez T. Shear bond strengths of different adhesive systems to white mineral trioxide aggregate. *Dental materials journal* 2009;28:62-7.
18. Kayahan MB, Nekoofar MH, Kazandag M, Canpolat C, Malkondu O, Kaptan F, et al. Effect of acid-etching procedure on selected physical properties of mineral trioxide aggregate. *Int Endod J* 2009;42:1004-14.
19. Shin J-H, Jang J-H, Park SH, Kim E. Effect of mineral trioxide aggregate surface treatments on morphology and bond strength to composite resin. *Journal of endodontics* 2014;40:1210-6.
20. Giuliani V, Nieri M, Pace R, Pagavino G. Effects of pH on surface hardness and microstructure of mineral trioxide aggregate and Aureoseal: an in vitro study. *J Endod* 2010;36:1883-6.
21. Nekoofar MH, Aseeley Z, Dummer PMH. The effect of various mixing techniques on the surface microhardness of mineral trioxide aggregate. *International Endodontic Journal* 2010;43:312-20.
22. Kaup M, Schafer E, Dammaschke T. An in vitro study of different material properties of Biodentine compared to ProRoot MTA. *Head Face Med* 2015;11:16.

23. Wang Z, Ma J, Shen Y, Haapasalo M. Acidic pH weakens the microhardness and microstructure of three tricalcium silicate materials. *International endodontic journal* 2015;48:323-32.
24. Perdigão J, Sezinando A, Monteiro PC. Effect of substrate age and adhesive composition on dentin bonding. *Operative dentistry* 2013;38:267-74.
25. Isolan CP, Valente LL, Münchow EA, Basso GR, Pimentel AH, Schwantz JK, et al. Bond strength of a universal bonding agent and other contemporary dental adhesives applied on enamel, dentin, composite, and porcelain. *Applied Adhesion Science* 2014;2:1-10.
26. Sanares AME, Itthagarun A, King NM, Tay FR, Pashley DH. Adverse surface interactions between one-bottle light-cured adhesives and chemical-cured composites. *Dental Materials* 2001;17:542-56.
27. Shokouhinejad N, Jafargholizadeh L, Khoshkhounejad M, Nekoofar MH, Raoof M. Surface microhardness of three thicknesses of mineral trioxide aggregate in different setting conditions. *Restorative dentistry & endodontics* 2014;39:253.
28. Malacarne J, Carvalho RM, Mario F, Svizero N, Pashley DH, Tay FR, et al. Water sorption/solubility of dental adhesive resins. *Dental materials* 2006;22:973-80.
29. Zecin-Deren A, Lukomska-Szymanska M, Szczesio-Wlodarczyk A, Piwonski I, Sokolowski J, Lapinska B. The Influence of Application Protocol of Simplified and Universal Adhesives on the Dentin Bonding Performance. *Applied Sciences* 2020;10:124.
30. Jang J-H, Lee MG, Woo SU, Lee CO, Yi J-K, Kim D-S. Comparative study of the dentin bond strength of a new universal adhesive. *Dental materials journal* 2016;35:606-12.
31. Takamizawa T, Barkmeier WW, Tsujimoto A, Berry TP, Watanabe H, Erickson RL, et al. Influence of different etching modes on bond strength and fatigue strength to dentin using universal adhesive systems. *Dental Materials* 2016;32:e9-e21.
32. Jayasheel A, Niranjana N, Pamidi H, Suryakanth MB. Comparative Evaluation of shear Bond Strength of universal Dental Adhesives-An in vitro study. *Journal of clinical and experimental dentistry* 2017;9:e892.

33. Torabinejad M, Hong C, McDonald F, Ford TP. Physical and chemical properties of a new root-end filling material. *Journal of endodontics* 1995;21:349-53.
34. Tian J, Zhang Y, Lai Z, Li M, Huang Y, Jiang H, et al. Ion release, microstructural, and biological properties of iRoot BP Plus and ProRoot MTA exposed to an acidic environment. *Journal of endodontics* 2017;43:163-8.
35. Maeda T, Yamaguchi K, Takamizawa T, Rikuta A, Tsubota K, Ando S, et al. pH changes of self-etching primers mixed with powdered dentine. *journal of dentistry* 2008;36:606-10.
36. Iwasa M, Tsubota K, Shimamura Y, Ando S, Miyazaki M, Platt JA. pH changes upon mixing of single-step self-etching adhesives with powdered dentin. *J Adhes Dent* 2011;13:207-12.

국 문 요 약

상아질 접착제의 산도가 Mineral Trioxide Aggregate 의 표면 미세경도에 미치는 영향

연세대학교 대학원 의학과

(지도교수: 김 지 훈)

임 윤 희

Mineral trioxide aggregate (MTA)는 생활치수치료와 천공 등에 쓰이는 생체 친화적인 치과재료이다. 하지만 긴 작업시간, 어려운 조작성, 치아 변색 등의 단점이 존재한다. MTA 에 의한 치아 변색을 예방하기 위해 상아질 접착제를 사용한 연구들이 있다. MTA 의 표면 경도가 산도에 의해 영향을 받는다는 것은 알려져 있지만, 상아질접착제의 산도가 MTA 의 표면 경도에 미치는 영향에 대해 연구가 이루어진 바 없다. 본 연구에서는 상아질 접착제의 산도에 따라 MTA 의 표면 미세경도에 미치는 영향에 대해 연구하고자 한다.

40 개의 원통형 몰드 (내경 3 mm, 높이 5 mm)을 준비하였다. 몰드 내면에 산도가 다른 3 개의 상아질 접착제 Adper Single Bond 2 (ASB), Single Bond

Universal (SBU), Clearfil SE bond 2 (CSE)를 적용하였다. 상아질 접착제를 적용하지 않은 군을 대조군으로 설정하였다. 상아질 접착제 적용 후 MTA 를 제조사의 지시에 따라 혼합 후 다져 넣고 젖은 면구와 함께 4 일간 보관하였다. MTA 경화 확인 후 몰드 내면으로부터 200, 400, 600 μm 지점에서 비커스 표면 경도 시험을 시행하였다. 95% 유의수준 하에 일원배치분산분석법 (one-way ANOVA)으로 통계적 유의차 검정하였으며, Tukey HSD 사후 검정을 시행하였다.

각 그룹의 평균 표면 미세경도는 각각 67.02 ± 11.38 (대조군), 48.76 ± 11.33 (ASB), 37.84 ± 9.36 (SBU), 43.78 ± 11.19 (CSE)였다. 3 개의 실험군은 대조군에 비해 낮은 표면 미세경도를 나타냈다 ($p < 0.001$). ASB 군과 SBU 군 사이에는 통계적 유의차가 있었다 ($p < 0.001$). SBU 군과 CSE 군 사이에는 통계적 유의차는 없었다. 각 그룹 내에서 지점에 따른 유의차는 없었다 ($p > 0.05$).

본 연구의 결과에 의하면, MTA 경화 전 상아질 접착제의 사용은 MTA 의 표면 미세경도를 낮출 수 있으며, 상아질 접착제의 산도가 낮을수록 MTA 표면 미세경도가 낮아질 것으로 예상된다.

핵심 되는 말: Mineral trioxide aggregate(MTA), 상아질 접착제, 산도, 비커스 표면 미세경도, 변색